

# Enhancement of Physico-Mechanical Characteristics of Graphene Nano Sheets Reinforced Cement

M. M. Mokhtar<sup>a</sup>, S. A. Abo-El-Enein<sup>b</sup>, M. Y. Hassaan<sup>c</sup>, M. S. Morsy<sup>a</sup>, M. H. Khalil<sup>a</sup>

<sup>a</sup>Housing and Building Research Center, HBRC, Building Physics Institute, Cairo, Egypt.

<sup>b</sup>Chemistry Department, Faculty of Science, Ain Shams University, Cairo, Egypt.

<sup>c</sup>Physics Department, Faculty of Science, AlAzhar University, Cairo, Egypt.

## **Abstract:**

**G**raphenenanosheets (GNSs) have unique physical properties that make them effective reinforcing materials. The attractive properties of graphene have led to enhance the graphene-polymer nanocomposites. This study investigates the effect of (GNSs) reinforcement on mechanical properties, pore structure and electrical characteristics of the hardened cement composites. GNS were added at different percentages of 0, 0.01, 0.02, 0.03, 0.04 and 0.05 wt. % of cement. Compressive strength was determined at 28 days of curing. Thermo-gravimetric analysis (TGA) was used to detect the phase decomposition, the pore structure was studied using nitrogen adsorption at 77.35°K technique, the microstructure was examined using scanning electron microscopy (SEM), and finally, electrical conductivity of graphene-cement composites was also studied. Results revealed that, considerable enhancements in compressive strengths by about 33% have been achieved by incorporating GNSs into cement matrix by about 0.04%. The integration of graphene into cement has significantly reduced the pore size of the pastes and led to a considerable improvement in the microstructure, with a consequent improvement in the electrical conductivity of these composites.

**Keywords:** Graphenenanosheets, Cement paste, Mechanical strength, pore structure, Thermal analysis, electrical properties.

## I. INTRODUCTION

Cementitious materials are the most widely utilized for many decades for different sorts of structures [1]. Although; cement based materials are used over a wide range of a structural applications, they are brittle and possess poor tensile strength. The brittleness of cement structures comes from the inferior characteristics of the cement pastes in the hardened state [2]. Enhancing the strength of cement materials generally can be achieved by using reinforcing microfibers, such as steel fibers [3], carbon fibers [4] polymeric fibers [5, 6] and natural fibers [7]. These reinforcing materials can greatly improve the strength characteristics as a whole and increase the stress at which cement starts to crack, i.e. they delay the crack growth in the cementitious matrix however do not inhibit the crack formation [8].

Nowadays, nanotechnology (NT) has provided nano-scale particles /fibers; including, nano silica (NS), carbon nano tubes (CNTs) and nanographene oxide (NGO); these might be utilized as reinforcements to inhibit the formation and delay the propagation of micro cracks. The use of nano fibers for improving the mechanical performance of cementitious materials are found to be more efficient than ordinary steel fibers (at millimeter scale) as they help in restricting cracks before they develop into microcracks. NS and nanometakaoline were found to enhance the mechanical performance of cement-based materials [9-14].

Nowadays, great attention was paid to graphene and graphene oxide nanoplatelets (GONPs) being the most beneficial nano reinforcing materials. It is used as a nano reinforcement in different matrices like polymer, ceramic or cement for improving their mechanical and electrical properties [15].

The characteristics of graphene oxide (GO) - cement composites were studied by some researchers; the introduction of GO by 0.05 wt.% of cement has increased the compressive strength considerably by 15 – 33%; in addition, an enhancement of about 41–59% has been achieved in the flexural strength [2], the incorporation of GONPs by 0.03 wt.% of cement can enhance the compressive strength of GO – cement composite and tensile strength by more than 40%; also the total porosity (TP) of cement paste decreased [16]. When GO was added to plain cement and cement mortar at different percentages 0.01, 0.02, 0.03, 0.04 and 0.05 wt.% of cement, significant improvements in the flexural and compressive strengths of the hardened cement pastes by about 90.5 and 40.4% have been attained at 28 days of hydration, respectively. The flexural and compressive strengths of cement mortar modified with GO at ratios of 0.01, 0.03 and 0.06% increased by 70.5 and 24.4 wt.% after 28 days of hydration, respectively [17]. Incorporating graphene into geopolymers at concentrations of 0.00, 0.10, 0.35 and 0.50% by weight has improved the microstructure and resulted in pore free condensed composites with enhanced mechanical performance, previous work reported an enhancement in flexural strength and Young's modulus by 134 and 376%, respectively [18].

It was found from the literature survey that, there are many conflicts regarding the development of GONPs/graphene reinforced cement especially in the GO/graphene incorporation ratios and the percentages of enhancements achieved. The

main issue to be addressed in this work is to add an extended study to investigate the role of graphene in enhancing the physical properties of hydrated cement by using different analytical techniques.

## II. EXPERIMENTAL PROGRAM

### 2.1. Preparation of Graphene nanosheets

Graphene Oxide (GO) was synthesized according to the modified Hummer's technique [19]. Typically, add 1 g of graphite + 0.5 g of  $\text{NaNO}_3$  in a flask, then add 50 ml of  $\text{H}_2\text{SO}_4$  (98%) under constant stirring at  $5^\circ\text{C}$  for 1h, after that, add gradually 3 g of  $\text{KMnO}_4$  (1g every 15 min.) taking into consideration that, the temperature of the solution have to be less  $20^\circ\text{C}$  to avoid overheating and explosion. Dilute the solution by slowly adding 100 ml warm distilled water, and then treat the solution with 3 ml of 30%  $\text{H}_2\text{O}_2$  solution and 100 ml of distilled water to be sure that,  $\text{KMnO}_4$  is completely reacted. After that, wash the mixture with HCl and water, respectively, then filtrate and dry to get GO, as a final step GO was thermally reduced for 6 hours to eliminate oxygen functionalities from the surface of GO to get the final product graphene sheets.

### 2.2. Preparation of cement composites

In this investigation, six mixes of cement-Graphene composites were studied. GNSs were added to ordinary Portland cement (OPC) by different ratios 0, 0.01, 0.02, 0.03, 0.04 and 0.05% by weight of cement. Firstly the as prepared GNSs were dispersed in the mixing water through ultrasonication process (at 250 Watt and frequency of 20 KHz) for 20 min. to be sure of good dispersion and to prevent agglomeration of GNSs. Now the mixing water with Graphene sheets dispersed in it can be added to cement to prepare the cement composites. The chemical composition of the used OPC is presented in table (1), while the mix composition was presented in Table (2).

Table (1): the chemical composition of OPC

$\text{SiO}_2$	$\text{Al}_2\text{O}_3$	$\text{Fe}_2\text{O}_3$	CaO	MgO	$\text{SO}_3$	L.O.I.	$\text{Na}_2\text{O}$	$\text{K}_2\text{O}$	Total
21.54	4.02	2.93	61.82	1.59	3.48	3.64	0.42	0.25	99.69

Table (2): Mix design of cement – nanographene composites

Mix designation	OPC, (%)	GNSs, (%)	W/C ratio
A	100	0	0.25
D1		0.01	0.26
D2		0.02	
D3		0.03	
D4		0.04	
D5		0.05	

The cement composite pastes were casted into 20 mm cubes for compressive strength test. The molds were vibrated for 1 min. to eliminate any contained air bubbles. The fresh pastes were kept in their molds at 100% relative humidity for 24 h, and then the samples were demolded and cured under tap water for 28 days [2].

## III. TESTING

### 3.1. Compressive strength

The Compressive strength of the samples was performed after 28 days of hydration on 20 mm cubic specimens as per a previous study for cement pastes [20] using RMU testing equipment hosted in HBRC, 57-2400 BERGAMO ITALY using loading rate 0.5 kn/sec. with a maximum force 1500 kn. Three specimens at each age were tested and the average compressive strength was calculated.

### 3.2. SEM

The microstructure of the freshly fractured surface of the specimens was examined using environmental scanning electron microscope (ESEM-Inspect S, FEI Company, Holland) equipped with Energy-dispersive X-ray analysis (EDX).

### 3.3. Thermal analysis

Thermogravimetric analyses of the samples were conducted using a DSC-TGA thermal analyzer (STD-Q600, USA) instrument from  $25^\circ\text{C}$  up to  $1000^\circ\text{C}$  at a heating rate of  $10^\circ\text{C}/\text{min}$ . The sample chamber was purged with nitrogen gas at a flow rate of 100 ml/min.

### 3.4. Pore structure

The Nitrogen adsorption - desorption isotherms were obtained for the hardened pastes of GO blended cement composites at  $77.35^\circ\text{K}$  using a NOVA 2000e (Quantachrome, USA) instrument. The pore-size distribution curves were obtained using nonlocal density function theory (NLDFT) kernel.

### 3.5. Electrical conductivity

For the electrical conductivity measurements, pellets with thickness of 3mm and 10mm diameter were prepared, see Fig.1. A programmable automatic RLC bridge, model Hioki 3532 Hitester, was used for these measurements. The parameters such as phase angle  $\phi$ , impedance  $Z$ , resistance  $R$  and capacitance  $C$  were measured in the applied range of frequencies 42 Hz – 5 MHz. The conductivity,  $\sigma$ , is calculated from the relation:

$$\sigma = \frac{d}{AZ} \quad (1)$$

Where:  $A$  is the cross-sectional area and  $d$  is the thickness of the pellet [21].



Fig. (1): Samples for electrical measurements

## IV. RESULTS AND DISCUSSION

### 4.1. Compressive strength

Fig.(2) shows the compressive strength results of the cured OPC pastes with different graphene additions. Evidently, the compressive strength of the hardened specimens increase with increasing GNSs percentage up to 0.04%, by further increase weight of GNSs dosage in OPC leads to a gradual decrease in the compressive strength. As shown in this figure, specimens containing 0.04 wt.% GNSs exhibited about 33.24% increase in compressive strength compared with that of the control OPC samples, that can be explained by improvement in mechanical interlocking caused by wrinkled appearance of graphene sheets, strong interaction between cracks and graphene due to the 2D sheet – like structure and high aspect ratio, enhancement of the hydration process [2] and the reduction of the pore structure in cement composite [16]. Also the gradual decrease may be interpreted by the agglomeration of the GNSs that result in difficulty to achieve uniform distribution of GNSs throughout the cement matrix.

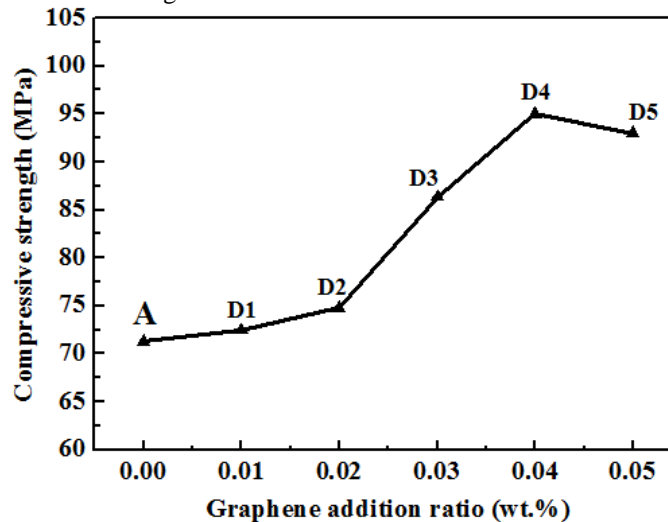


Fig. (2): Compressive strength of the hardened specimens made of OPC with different GNSs additions, after 28 days of curing.

### 4.2 Pore structure analysis

The hardened cement paste is composed of the solid part of hydrated cement and the pores. There are different reasons for the presence of pores in the hardened cement paste among them the excess water and air. These pores affect the strength, durability and shrinkage. In this study, the pore sizes and their distribution was determined by nitrogen adsorption technique. There are four main pore size distribution categories in cement paste: pores of size  $>1000$  nm are called large pores, capillary pores are of size between 100 to 1000 nm, meso – pores or transitional pores have size ranges from 10 to 100 nm and finally the gel pores have size  $<10$  nm. Based on this classification, the pores in our samples are mainly meso-pores and gel pores. Moreover, macroscopic pores ( $>50$  nm) contribute to permeability and strength, while microscopic pores ( $<50$  nm) may affect the dry shrinkage and creep [22,23].

Results of Fig.(3) indicate that, the addition of GNSs can efficiently improve the pore structure, through reducing the pore size and making the cement paste more compact. The GNSs concentration of 0.04wt.% yielded the lowest intensity in the pore size distribution and consequently, the highest compressive strength values; the intensity of the peak is an indication for the number of pores having the transitional pore size (meso- pores) and the location of the peak represents the sizes of these pores. Therefore, the addition of 0.04% graphene resulted in a decrease in the number of transitional pores (meso - pores).

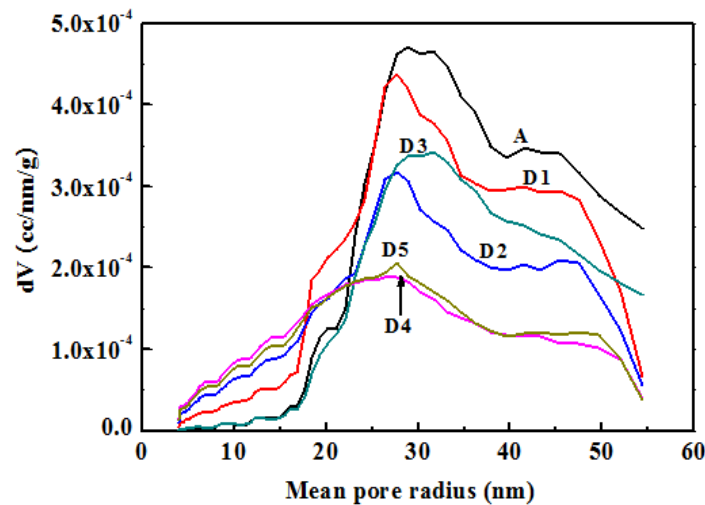


Fig. (3) Pore- size distribution curves of cement-graphene composites, after 28 days of curing

#### 4.3 Thermogravimetric analysis (TGA)

TGA was used to estimate the thermal stability of the prepared samples. Fig. (4) represents the thermograms of cement paste reinforced with different graphene ratios in comparison with the plain cement mix (A). It can be noticed that, all the steps characterizing the calcium hydroxide (CH) and calcium carbonate (CC) phases of the prepared blended mixes are shifted to higher temperature relative to the plain mix (without GO/graphene) which confirms that the thermal stability of the hydration products increased by the addition of graphene sheets.

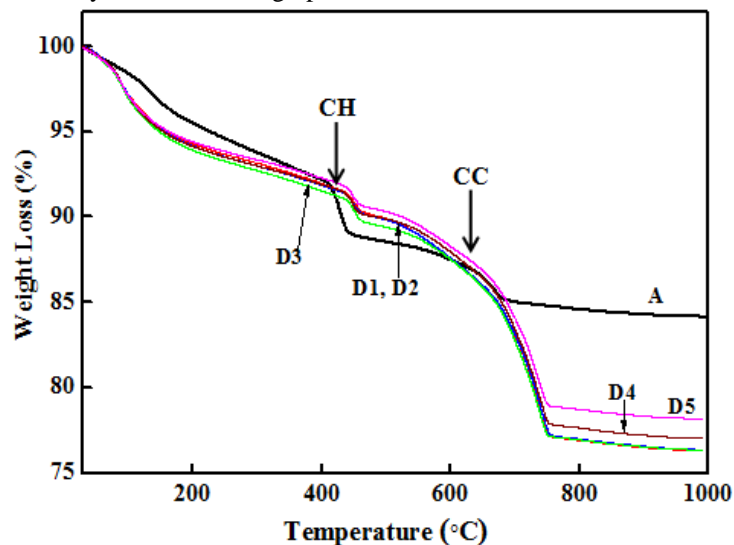


Fig. (4): The TGA thermograms of graphene-cement composites, after 28 days of curing.

#### 4.4. Morphology and microstructure

The mechanical properties of cementitious materials are determined by their microstructure characteristics. In order to determine the reasons of mechanical strength improvements and to get visual evidence of the microstructural characteristics responsible for these improvements, the morphology and microstructure was performed for the graphene-cement composites as presented in Figs. (5, 6). The SEM micrograph of plain mix (OPC) revealed non-uniform distribution of the hydrated phases; furthermore, macropores and microcracks are observed as shown in Fig.5(A, B). The addition of GNSs has generally modified the microstructure and resulted in more uniform and compact structure as they cause bridging (2D reinforcement) between cement hydrates as presented in Figs.6(A, B). Evidently, the microstructure of the hardened specimens made of OPC - GONPs composites displayed the formation of interlocking fibers and wrinkled foils of CSH; so the number of binding centers in the hardened specimens increased leading to an increase in the hydraulic properties of these specimens. The microstructure obtained for the specimens made until 0.02% addition of GONPs appeared to have larger points of contact in C-S-H, leading to the maximum improvement of the mechanical

properties; this provides a strongly hydraulic structure having an increase in the total contents of binding centers. Furthermore, Nucleation of hydration products on nanoparticles further promotes and accelerates cement hydration and results in enhanced strength [24, 25].

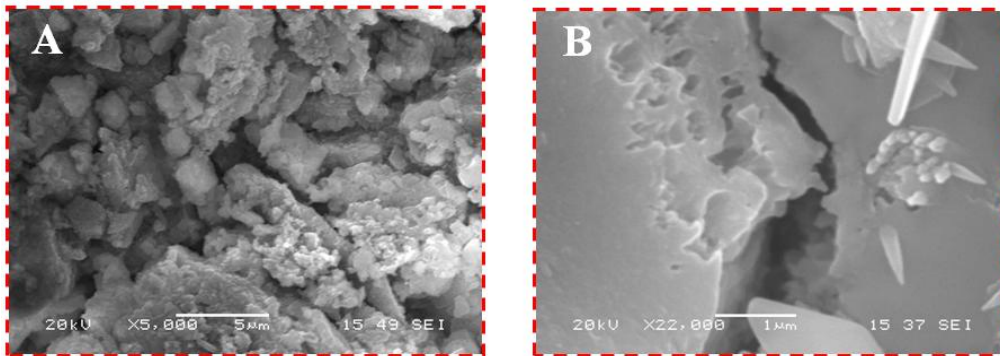


Fig.(5):SEM images of plain cement paste, taken after 28 days of curing

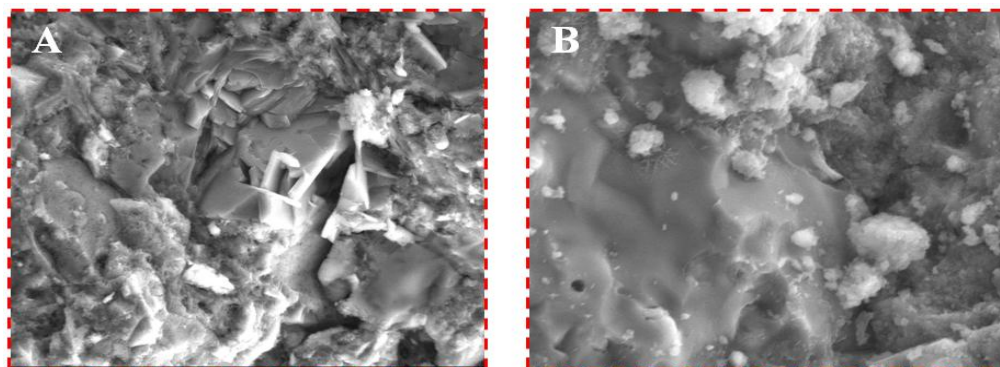


Fig.(6):SEM images of cement paste modified with graphene sheets, taken after 28 days of curing

#### 4.5. Electrical conductivity

Electrical conductivity of cement paste occurs primarily due to ion transport through the pore solution in the cement based system [26]. During hydration, the capillary pores in the cement are gradually filled up with hydration products such as C-S-H, CH, ettringite and the conductivity decreases with increasing hydration time.

Graphene and its derivatives are used to enhance the electrical conductivity of cement composites.

In this study, the specimens tested were oven dried to avoid the ionic conduction. As a result, the conduction that was observed probably was due to the electronic conduction.

**Fig. (7)** shows the electrical conductivity of neat cement paste as a function of frequency (42 Hz – 5 MHz ), it is observed that the conductivity of the neat cement paste reached about  $3.19 \times 10^{-8} \Omega^{-1} \text{cm}^{-1}$ , while **Fig. (8)** presents the electrical conductivity of cement composites reinforced with different ratios of graphene in comparison with the conductivity of neat cement paste, from these figures; it was observed that, the highest conductivity was  $9.4 \times 10^{-6} \Omega^{-1} \text{cm}^{-1}$  for composite D2, which means that, the incorporation of graphene greatly enhanced the electrical conductivity of cement pastes.

#### V. CONCLUSIONS

The influence of GNSs dosage on the microstructural characteristics, mechanical performance and electrical conductivity of cement composites were investigated. The results indicated that:

- In contrast to many previous studies it can be concluded that, small ratios of GNSs about 0.02-0.04% can enhance the physico-mechanical characteristics of hardened OPC – GNSs composite pastes.
- The addition of GNSs in cement paste significantly increases the compressive strength. The addition of 0.04% GNSs increased the compressive strength by about 33%.
- GNSs modified the pore structure, through reducing the number of pore and making the cement paste more compact and strongly hydraulic.
- GNSs increase the degree of thermal stability of the hydration products especially of CH and CC phases.
- Finally, the electrical conductivity of cement pastes markedly enhanced by the addition of graphene nanosheets.

#### ACKNOWLEDGEMENT

We are grateful to Housing and Building Research Center (HBRC), Physics department of Al Azhar University.

#### REFERENCES

- [1] B. Han, X. Yu, J. Ou, Multifunctional and Smart Carbon Nanotube Reinforced Cement-Based Materials, Nanotechnology in Civil Infrastructure (2011), 1-47.

- [2] Z. Pan, L. He, L. Qiu, A. H. Korayem, G. Li, J. W. Zhu, F. Collins, D. Li, W. H. Duan, M. C. Wang, Mechanical properties and microstructure of a graphene oxide–cement composite, *Cem. Concr. Compos.* 58 (2015) 140–147.
- [3] K. Watanabe, K. Toshihide, N. Junichiro, Synergetic effect of steel fibers and shear-reinforcing bars on the shear-resistance mechanisms of RC linear members, *Constr. Build. Mater.* 24 (2010) 2369–75.
- [4] M.d Z. Hossain., A. S. M. Abdul Awal., Flexural response of hybrid carbon fiber thin cement composites, *Constr. Build. Mater.* 25 (2011) 670–7.
- [5] A. Majid, L. Anthony, S.Hou, C. Nawawi, Mechanical and dynamic properties of coconut fibre reinforced concrete, *Constr. Build. Mater.* 30 (2012) 814–25.
- [6] S. Parviz, W. Jong-Pil, H. Maan, Durability characteristics of CO<sub>2</sub>-cured cellulose fiber reinforced cement composites, *Constr. Build. Mater.* 34 (2012) 44–53.
- [7] H. Su, J. Xu, Dynamic compressive behavior of ceramic fiber reinforced concrete under impact load, *Constr. Build. Mater.* 45 (2013) 306–13.
- [8] P.K. Nelson, V.C. Li, T. Kamada, Fracture toughness of microfiber reinforced cement composites, *J Mater. Civ. Eng.* 14(5) (2002) 384–91.
- [9] M. S. Morsy, S. H. Alsayed and M Agel, Hybrid Effect of Carbon Nanotube and nano clay on Physico-Mechanical Properties of Cement Mortar, *Constr. Build. Mater.* 25 (2011) 145-149.
- [10] H. Shoukry, M.F. Kotkata, S.A. Abo-el-Enein, M.S. Morsy, Flexural strength and physical properties of fiber reinforced nanometakaolincementitious surface compound, *Constr. Build. Mater.* 43 (2013) 453–460.
- [11] A.E. AL-Salami, M.S. Morsy, S. Taha and H. Shoukry, Physico-mechanical characteristics of blended white cement pastes containing thermally activated ultrafine nanoclays, *Constr. Build. Mater.* 47 (2013) 138–145.
- [12] M. S. Morsy, Y. Al-Salloum, T. Almusallam and H. Abbas, Effect of nano-metakaolin addition on the hydration characteristics of fly ash blended cement mortar, *J Therm. Anal. Calorim.* DOI 10.1007/s10973 (2013) 3512-6.
- [13] H. Shoukry, M.F. Kotkata, S.A. Abo-EL-Enein, M.S. Morsy, S.S. Shebl, Enhanced physical, mechanical and microstructural properties of light weight vermiculite cement composites modified with nanometakaolin, *Constr. Build. Mater.* 112 (2016) 276–283.
- [14] B.W. Jo, C.H. Kim, G.H. Tae, J.B.Park, Characteristics of Cement Mortar with Nano-SiO<sub>2</sub> Particles, *Constr. Build. Mater.* 21(6) (2007) 1351-5.
- [15] Properties and Applications of Graphene Oxide and Functionalized Graphene. <http://www.azonano.com/article.aspx?ArticleID=4044>; Sponsored by Graphenea; 2015.
- [16] K. Gong, S.M.ASCE, Z. Pan, A. H. Korayem, Ph.D., L. Qiu, D. Li, F. Collins, C. M.Wang, W. H. Duan, A.M. ASCE, Reinforcing Effects of Graphene Oxide on Portland Cement Paste, *J. Mater. Civ. Eng.* 2015.
- [17] Q. Wang, J. Wang, C. x. Lu, B. w. Liu, K. Zhang, C. z. Li, Influence of graphene oxide additions on the microstructure and mechanical strength of cement, *New Carbon Mater.* 30(4) (2015) 349-356.
- [18] M. Saafi, L. Tang, J. Fung, M. Rahman, J. Liggat, Enhanced properties of graphene/fly ash geopolymeric composite cement, *Cem. Concr. Res.* 67 (2015) 292–299.
- [19] L. Shahriary, A. A. Athawale, Graphene Oxide Synthesized by using Modified Hummers Approach, *Int. J. Renew. Energy Environ. Eng.* 02(01) (2014) ISSN 2348-0157.
- [20] Mohamed Heikal, M. S. Morsy, Ismail Aiad, effect of polycarbxylate super plasticizer on hydration characteristics of cement pastes containing silica fume, *ceramics silikaty*, 50 (1), (2006), 5-14.
- [21] M.M. El-Nahass, H.A.M. Ali, M. Saadeldin, M. Zaghllol, AC conductivity and dielectric properties of bulk tungsten trioxide (WO<sub>3</sub>), *Physica B* 407 (2012) 4453–4457
- [22] Q. Zeng, K. Li, T. Fen-chong, Pore structure characterization of cement pastes blended with high-volume fly-ash [J]. *Cem. Concr. Res.* 42(1) (2012) 194-204.
- [23] J. L. Provis, R. J. Myers, C. E. White, X-ray microtomography shows pore structure and tortuosity in alkali-activated binders [J]. *Cem. Concr. Res.* 42(6) (2012) 855-864.
- [24] S. Chakraborty, S.P. Kundu, A. Roy, B. Adhikari, S.B. Majumder, Effect of jute as fiber reinforcement controlling the hydration characteristics of cement matrix, *Ind. Eng. Chem. Res.* 52 (2013) 1252–60.
- [25] F. Babak, H. Abolfazl, R. Alimorad, G. Parviz, Preparation and Mechanical Properties of Graphene Oxide: Cement Nanocomposites, *Sci. World J.* 2014, Article ID 276323.
- [26] Topçu, İ. B., Uygunoğlu, T. & Hocaoğlu, İ., Electrical conductivity of setting cement paste with different mineral admixtures, *Construction and Building Materials*, 28(1), (2012), 414-420